

TECHNICAL DATA SHEET

My-T-Lok® 250

Flexible Gasket

January 2017



METLOK PRIVATE LIMITED
(An ISO 9001 Certified Company)
W-27, M.I.D.C., Industrial Area
Kalmeshwar – 441 501, Nagpur

Product Description

My-T-Lok® 250 is a flexible gasket. It cures when confined in the absence of air between close fitting metal surfaces. It seals close fitting face joints between surfaces with high thermal expansion property e.g. Aluminum to CI joint.

Special Feature:

- ❖ Provides resistance to low pressures immediately after assembly of flanges.
- ❖ This product may be dispensed robotically with the appropriate product conditioning and dispensing systems.
- ❖ Maintains flexibility after exposure to high temperature.

Applications:

- ❖ My-T-Lok® 250 used as a form-in-place gasket on rigid flanged connections, e.g. gearbox and engine casings etc.

Properties


Technology	: Acrylic
Chemical Type	: Urethane methacrylate
Components	: One component
Appearance	: Red / Dark Purple paste
Specific Gravity @ 25 °C	: 1.13
Viscosity @ 25±2 °C, Brookfield, Spindle # 6, Speed 10 r.p.m.	: 100000 -150000 cP
Cure	: Anaerobic
Secondary Cure	: Activator
Strength	: Medium
Service Temperature	: -50 °C to 150 °C
Application	: Gasket and Sealant

Curing Performance

The product cures when confined in the absence of air between closed fitting metal surfaces. Although functional strength is developed in a relatively short time, curing continues for at least 72 hours before full chemical/solvent resistance is developed.


Cure Speed vs. Substrate

The rate of cure will depend on the substrate used. The graph below shows the shear strength developed with time on steel lap shears compared to different materials and tested according to ASTM D 1002.

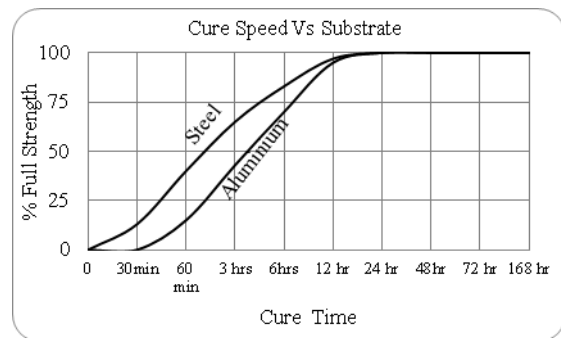

Cure Speed vs. Temperature

The rate of cure will depend on the ambient temperature. The graph below shows the shear strength developed with time on steel lap shears at different temperatures and tested according to ASTM D 1002.

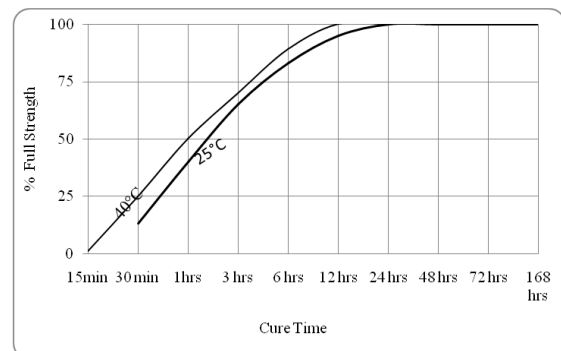


Cure Speed vs. Activator

Where cure speed is unacceptably long due to large gaps, applying activator to the surface will improve cure speed. However, this can trim down ultimate strength of the bond and therefore testing is recommended to confirm effect.

The graph below shows the shear strength developed with time on steel lap shears using

different activators and tested according to ASTM D 1002.

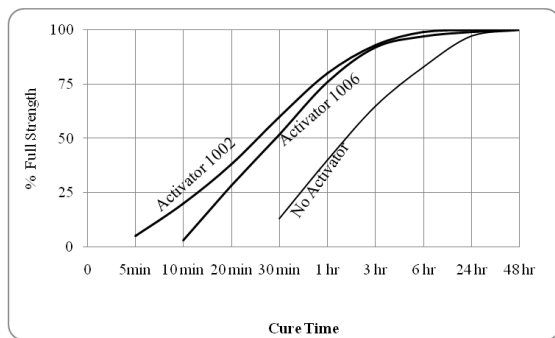

Adhesive Properties of Cured Material

Lap Shear Strength, ASTM D 1002 ;After 24 hrs @ 25±2 °C

Steel : ≥ 2 N/mm²
Aluminum : ≥ 2 N/mm²

Tensile Strength, ASTM D-897 ; After 24 hrs @ 25±2 °C

Steel : ≥ 3 N/mm²
Aluminum : ≥ 2 N/mm²

Compressive Shear Strength, BIS 13055:1991;
After 24 hrs @ 25±2 °C
Steel Pins and Collars : ≥ 4 N/mm²

Lap Shear Strength, ASTM D 1002 ;After 72 hrs @ 25±2 °C

Steel : ≥ 7 N/mm²
Aluminum : ≥ 7 N/mm²

Lap Shear Strength, ASTM D 1002 ;After 168 hrs @ 25±2 °C

Steel : ≥ 7 N/mm²
Aluminum : ≥ 8 N/mm²

Sealing Capability

An annular shaped gasket with an inner diameter of 60 mm and an external diameter of 90 mm was tested up to 100 bars, hydraulic pressure, for pressure drop, after 24 hrs (BIS 13055:1991).

No Induced Gap : No Drop
Induced Gap;0.25 mm : No Drop

Instant Sealing Capability

My-T-Lok 250 has the ability to resist low on-line test pressures while still uncured. This test was performed immediately after assembly of an annular shaped Steel flange before cure set in by applying *pneumatic* pressure. The pressure was maintained for 1 minute.


Pressure Resistance, bars

Induced Gap 0.00 mm : 5
Induced Gap 0.1 mm : 2
Induced Gap 0.25 mm : 0.5

Hot Strength

Test : Lap Shear Strength, ASTM D 1002
Substrate : Steel
Cure : 24 hrs @ 25±2 °C


Tested at temperature indicated

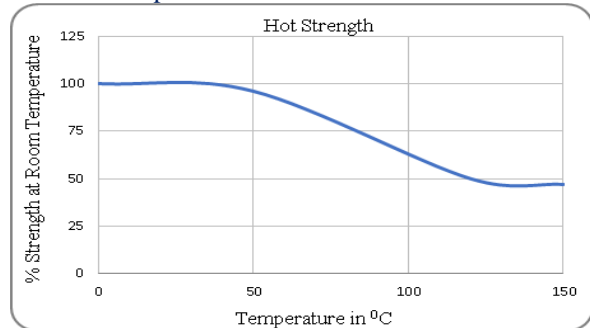

Heat Aging

Test : Lap Shear Strength, ASTM D 1002
Substrate : Steel
Cure : 24 hrs @ 25±2 °C

Aged at temperature indicated and tested @25±2 °C.

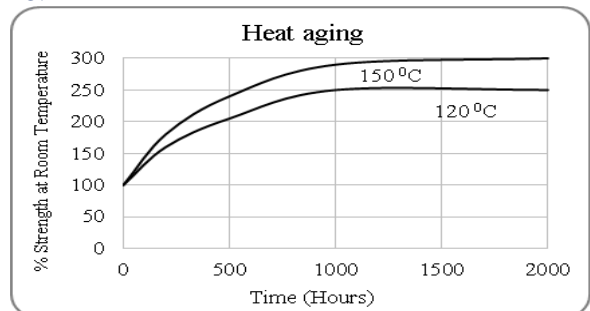

Chemical/Solvent Resistance

Test : Lap Shear Strength, ASTM D-1002
Substrate : Steel
Cure : 24 hrs @ 25±2 °C

Aged under condition indicated and tested @25±2 °C.

Environment	Temp (°C)	% of initial strength	
		168 hrs	500 hrs
Engine Oil	120	100	180
Gear oil	120	100	110
Water Glycol (50/50)	87	100	120
Unleaded Petrol	25±2	100	140
Diesel	25±2	100	150

Directions for Use

1. For best performance bond surfaces should be clean and free from grease.
2. The product is designed for close fitting flanged parts.
3. Apply manually as a continuous bead to one surface of the flanges.
4. Low pressures may be used when testing to confirm a complete seal immediately after assembly and before curing.
5. Flanges should be assembled and tightened as soon as possible after assembly to keep away from shimming.
6. Clean excess adhesive.

Handling

- ❖ For safe handling My-T-Lok® 250 must be handled in a manner as indicated in Material Safety Data Sheet (MSDS) and in compliance with relevant local regulations.
- ❖ My-T-Lok® 250 is not recommended for use in pure oxygen and/or oxygen rich systems and should not be selected as a sealant for chlorine or other strong oxidizing materials
- ❖ My-T-Lok® 250 can affect certain plastics particularly thermoplastic materials or coatings. It is recommended to check all surfaces for compatibility before use.
- ❖ Where aqueous washing systems are used to clean the surfaces before bonding, it is important to check for compatibility of the washing solution with the adhesive. In some cases these aqueous washes can affect the cure and performance of the adhesive.
- ❖ My-T-Lok® 250 is non-volatile and non-flammable at room temperature.

Storage

- ❖ Store My-T-Lok® 250 in a cool, dry and unopened container at 25±2°C.
- ❖ Store away from sunlight and heat sources.
- ❖ My-T-Lok® 250 will exhibit a shelf life of 18 months from the date of manufacture when stored in above mentioned conditions.
- ❖ To prevent contamination of unused product, do not return any material to its original container. For further specific shelf life information, contact our Technical Service center R&D Center.

Pack Size

My-T-Lok® 250 is ideally available in 250 ml and 1000 ml pack size.

Note

All statements, technical information and recommendations set forth herein are based on tests which Metlok Private Limited, believes to be reliable. However, Metlok Private Limited does not guarantee their accuracy or completeness. We cannot assume responsibility for the results obtained by others over whose methods we have no control. It is the user's responsibility to determine suitability for the user's purpose of any production methods mentioned herein and to adopt such precautions as may be advisable for the protection of property and of persons against any hazards that may be involved in the handling and use thereof. In no case will Metlok Private Limited be liable for direct, consequential economic or other damages.

METLOK PRIVATE LIMITED

(Bonding and Sealing Solutions)

An ISO 9001: 2015 Certified Company

Tel.: 07118-271543/271170/272468

Fax: 07118-272470

Visit us at: www.metlok.in